

Mineralogical characterisation of gem zircon from Ratanakiri, Cambodia

Wittwer, A.¹, Nasdala, L.^{1,*}, Wanthanachaisaeng, B.², Bunnag, N.², Škoda, R.³, Balmer, W.A.⁴, Giester, G.¹, Zeug, M.¹

¹Institut für Mineralogie und Kristallographie, Universität Wien,
Althanstr. 14, 1090 Wien, Austria

²Faculty of Gems, Burapha University, Chanthaburi 22170 Thailand

³Faculty of Science, Masaryk University, Kotlářská 2, 61137 Brno, Czech Republic

⁴Department of Geology, Faculty of Science, Chulalongkorn University,
Bangkok 10330, Thailand

*e-mail: lutz.nasdala@univie.ac.at

Heat treatment is commonly done to improve the colour of gemstones. In the case of gem zircon, the highly priced blue-coloured material is produced from reddish brown raw stones by heat-treatment under reducing conditions at ca. 1000 °C for several hours. Especially zircon from the Ban Lung and Bo Loi areas, Ratanakiri province, Cambodia, is susceptible to this colour change (Balmer et al. 2011). The cause of the blue colour, and the reason for the particularly rich colouration of the Ratanakiri material, are still controversial; these problems are currently addresses in a joint research conducted at Universität Wien and Burapha University, Chanthaburi. Here we report results of a preliminary study done to characterise the raw material and especially its structural state (i.e. degree of radiation damage).

The Ratanakiri gem zircon is extracted from sediments or gravels in numerous small mines, mostly from layers at ca. 2–15 metres below the Earth's surface. The zircon originates from young volcanic rocks (tholeiitic basalts or pyroclastic rocks) with ages in the range 0.8–4.3 Ma (Hoang et al. 1998; Rangin et al. 1995).

We have studied a series of large, gem-quality specimens that were first crystallographically oriented on a four-circle X-ray diffractometer. Specimens were cut in half along the crystallographic c-axis. One half was then subjected to heat treatment whereas the second half was left in its original state. Both halves were then prepared as doubly polished sections. This enabled us to analyse chemically end texturally equivalent specimens with matching faces, hence providing direct comparability of untreated (brown) and treated (blue) material.



Fig. 1. Image of a cut, gem-quality zircon specimen (size 17 mm). The right half was subjected to heat-treatment whereas the left half is in its initial state.

The Ratanakiri zircon was found to be relatively uniform in chemical composition, with generally low contents of non-formula elements. The HfO_2 content averages ca. 0.7 wt%, and the actinides U and Th have low concentrations of 40–240 ppm and 10–270 ppm, respectively. This results in a remarkably low time-integrated self-irradiation dose on the order of 10^{16} alpha-decay events per gram. Note that readily detectable radiation damage is observed after accumulation of $0.1\text{--}0.2 \times 10^{18}$ α/g , and complete metamictisation requires ca. $5\text{--}10 \times 10^{18}$ α/g (Nasdala et al. 2004, and references therein). The amount of radiation damage in the Ratanakiri zircon was correspondingly found to be negligible.

As a consequence, the heat treatment does not result in measurable structural reconstitution. Unit-cell constants, Raman spectral parameters, and widths of Nd^{3+} emissions obtained from untreated and treated samples are indistinguishable and do vary notably from data for synthetic ZrSiO_4 (Fig. 2). Reliable detection of colour enhancement appears hence difficult in case of the nearly non-radiation-damaged Ratanakiri material.

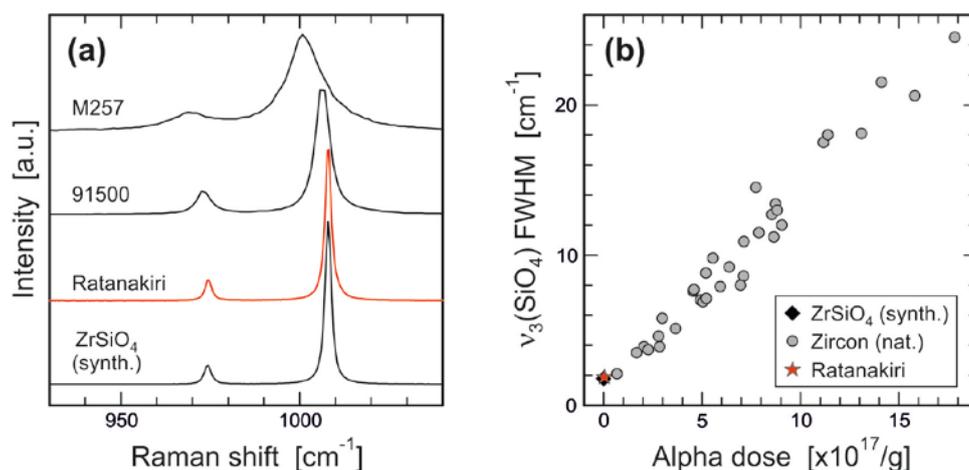


Fig. 2. (a) Raman spectrum of the Ratanakiri zircon in comparison with reference samples, including synthetic ZrSiO_4 , zircon 91500 (Wiedenbeck et al. 2004; mildly radiation-damaged) and M257 (Nasdala et al. 2008; moderately radiation-damaged). (b) Plot of the width of the main Raman band near 1000 cm^{-1} versus alpha dose (from Nasdala et al. 2004, modified). Note that spectral parameters of the Ratanakiri zircon are indistinguishable from those of synthetic ZrSiO_4 , indicating that the Ratanakiri zircon has accumulated extremely low amounts of radiation damage.

Acknowledgments: We thank W. Diegor, C. Lenz, M. Müller, C. Petautschnig, and M. Wildner for experimental assistance. Partial funding of this research by the ASEA Uninet is gratefully acknowledged.

References:

- Balmer WA, Smith MH, Sriprasert B, Wanthanachaisaeng B (2011) Ratanakiri, the legendary zircon province of Cambodia. Abstracts of GIA's 46th Gemstone Gathering, Bangkok, Thailand, May 25, 2011
- Hoang N, Flower MFJ (1998) Petrogenesis of Cenozoic basalts from Vietnam: implication for origins of a "diffuse igneous province". *J Petrol* 39:369–395
- Nasdala L, Reiners PW, Garver JJ, Kennedy AK, Stern RA, Balan E, Wirth R (2004) Incomplete retention of radiation damage in zircon from Sri Lanka. *Am Mineral* 89:219–231
- Nasdala L, Hofmeister W, Norberg N, Mattinson JM, Corfu F, Dörr W, Kamo SL, Kennedy AK, Kronz A, Reiners PW, Frei D, Košler J, Wan Y, Götz J, Häger T, Kröner A, Valley JW (2008) Zircon M257 – a homogeneous natural reference material for the ion microprobe U-Pb analysis of zircon. *Geostand Geoanal Res* 32:247–265
- Rangin C, Huchon P, Le Pichon X, Bellon H, Lepvrier C, Roques D, Hoe ND, Quynh PV (1995) Cenozoic deformation of central and south Vietnam. *Tectonophysics* 251:180–196
- Wiedenbeck M, Hanchar JM, Peck WP, Sylvester P, Valley J, Whitehouse MJ, Kronz A, Morishita Y, Nasdala L (2004) Further characterization of the 91500 zircon crystal. *Geostandard Newslett* 28:9–39